

## Unusual disorder effects in superconducting $\text{LaFeAs}_{1-\delta}\text{O}_{0.9}\text{F}_{0.1}$ as revealed by $^{75}\text{As}$ NMR spectroscopy

F. Hammerath,<sup>1</sup> S.-L. Drechsler,<sup>1</sup> H.-J. Grafe,<sup>1</sup> G. Lang,<sup>1</sup> G. Fuchs,<sup>1</sup> G. Behr,<sup>1</sup> I. Eremin,<sup>2</sup> M. M. Korshunov,<sup>2,3,\*</sup> and B. Büchner<sup>1</sup>

<sup>1</sup>*Institute for Solid State Research, IFW Dresden, P.O. Box 270116, D-01171 Dresden, Germany*

<sup>2</sup>*Max-Planck-Institut für Physik komplexer Systeme, D-01187 Dresden, Germany*

<sup>3</sup>*L.V. Kirensky Institute of Physics, Siberian Branch of Russian Academy of Sciences, 660036 Krasnoyarsk, Russia*

(Received 17 December 2009; revised manuscript received 15 March 2010; published 16 April 2010)

We report  $^{75}\text{As}$  nuclear magnetic resonance measurements of the spin-lattice relaxation in the superconducting (SC) state of  $\text{LaFeAsO}_{0.9}\text{F}_{0.1}$  and As-deficient  $\text{LaFeAs}_{1-\delta}\text{O}_{0.9}\text{F}_{0.1}$ . The temperature behavior of  $1/T_1$  below  $T_c$  changes drastically from a  $T^3$  dependence for  $\text{LaFeAsO}_{0.9}\text{F}_{0.1}$  to a  $T^5$  dependence for the As-deficient sample. These results, together with the previously reported unexpected increase in  $T_c$  and the slope of the upper critical field near  $T_c$  for the As-deficient sample, are discussed in terms of nonuniversal SC gaps in Fe pnictides and the effect of As deficiency as an exotic case where nonmagnetic “smart” impurities even stabilize an  $s_{\pm}$ -wave superconductor or within a scenario of a disorder-driven change to  $s_{++}$  superconductivity.

DOI: [10.1103/PhysRevB.81.140504](https://doi.org/10.1103/PhysRevB.81.140504)

PACS number(s): 74.70.Xa, 76.60.-k, 74.20.Rp

The symmetry of the order parameter and the underlying Cooper-pairing mechanism in the newly discovered Fe-based superconductors<sup>1</sup> are one of the most challenging problems in contemporary solid-state physics. Historically, nuclear magnetic resonance (NMR) studies showing up the so-called Hebel-Slichter peak in the nuclear spin-lattice relaxation rate (NSLRR) played a significant role in establishing the BCS theory as the first microscopic description of conventional (weakly coupled) superconductors.<sup>2</sup> Physically, this behavior is caused by the coherence factors and the symmetry of a single nodeless superconducting (SC) gap.<sup>3</sup> Nowadays, within a simplified approach (ignoring damping, strong coupling, anisotropy, impurity, and inhomogeneity effects<sup>4,5</sup>) its presence or absence together with the  $T$  dependence of the NSLRR,  $1/T_1$ , below  $T_c$  are frequently used to discriminate tentatively conventional from unconventional pairing. For a single Fermi-surface (FS) sheet and superconductivity in the clean limit  $T^3$  and  $T^5$  dependencies would be regarded as evidence for line- and point-node SC order parameters, respectively, which for singlet pairing correspond to the  $d$ -wave and a special  $s+g$ -wave state. Recently it has been realized that the situation in multibands and especially in Fe pnictides with impurities is far from being that simple, in particular, there is no universal behavior for the growing number of related compounds.<sup>6</sup> The  $s_{\pm}$  scenario proposed<sup>7-10</sup> at the early stages of the Fe-pnictide research at present is still the most popular one. Due to the vicinity of a competing spin-density-wave state in the phase diagram, it is tempting to assume that antiferromagnetic (AFM) spin fluctuations might be the dominant pairing glue. Then, from the FS topology given by small hole [electron] pockets centered around the  $\Gamma=(0,0)$  [ $M=(\pi,\pi)$ ] points of the Brillouin zone, a nodeless gap with opposite signs on each of the disconnected FS pockets separated by the wave vector  $\mathbf{Q}=(\pi,\pi)$  is naturally suggested.

With respect to pair-breaking interband impurity scattering some doubts about this sign-reversed  $s_{\pm}$  scenario have been put forward.<sup>11-17</sup> Also the available weak-coupling fits of the upper critical fields  $B_{c2}(T)$  for the Nd-1111, the Sm-

1111, and the La-1111 systems,<sup>18-20</sup> all closely related to the ones considered here, do not show a dominant interband pairing interaction generic for the intended  $s_{\pm}$  scenario but result at most in comparable intraband and interband coupling strengths or even in dominant intraband ones. Finally, for the two-gap system  $\text{FeSe}_{1-x}$  only a tiny interband coupling has been derived from the  $T$  dependence of the penetration depth.<sup>21</sup>

Various experiments have been carried out to extract the symmetry of the SC order parameter in Fe-based superconductors. In particular, angle resolved photoemission spectroscopy (ARPES) and microwave data<sup>22</sup> are consistent with a SC gap being nodeless on each FS pocket. These results taken together with the observation of a peak at the AFM wave vector  $\mathbf{Q}$  and  $\omega=\omega_{res}$  found below  $T_c$  in various compounds<sup>23</sup> by means of inelastic neutron-scattering (INS) experiments provide support in favor of  $s_{\pm}$ -wave symmetry. Note that a sharp resonance peak is a result of different signs of the SC gap for  $\mathbf{k}$  and  $\mathbf{k}+\mathbf{Q}$  points generic for the  $s_{\pm}$ -wave symmetry. However, it has been argued recently<sup>13</sup> that a somewhat broader peaklike feature can be attributed to a self-energy renormalization of quasiparticles in  $s_{++}$ -wave (sign preserved) superconductors. A similar feature in Raman spectra has not been observed.<sup>24</sup> Hence, the assignment of the observed INS features is controversial.

In this unclear situation we report  $^{75}\text{As}$  NMR measurements of the NSLRR in  $\text{LaFeAsO}_{0.9}\text{F}_{0.1}$  and As-deficient  $\text{LaFeAs}_{1-\delta}\text{O}_{0.9}\text{F}_{0.1}$ . Surprisingly we observe a drastic change in the  $T_1^{-1}(T)$  dependence below  $T_c$  from  $T^3$  for  $\text{LaFeAsO}_{0.9}\text{F}_{0.1}$  to  $T^5$  for  $\text{LaFeAs}_{1-\delta}\text{O}_{0.9}\text{F}_{0.1}$ . Comparing our NMR data with other available data, we discuss three alternative scenarios: (i) a nonuniversal superconducting gap, (ii) a disorder driven transition from  $s_{\pm}$ -wave to  $s_{++}$ -wave symmetry in Fe pnictides as well as (iii) the As deficiency as a rare case of defects which can yield even a stabilization of unconventional  $s_{\pm}$ -wave or conventional  $s_{++}$ -multiband superconductivity. Theoretical issues to be settled in (ii) and (iii) as well as further experiments to clarify the challenging situation are proposed.

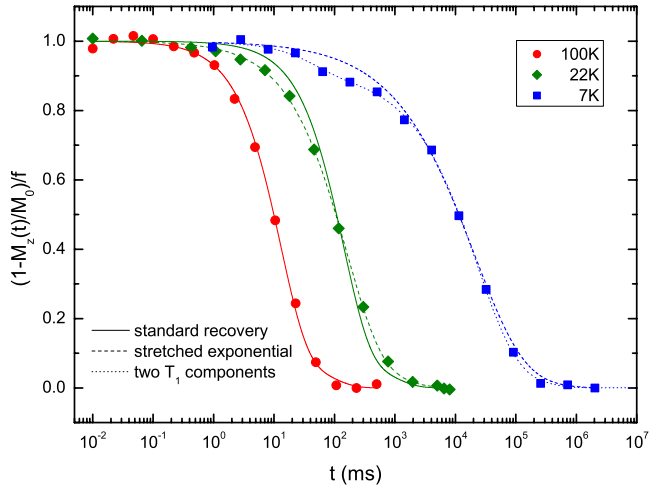


FIG. 1. (Color online) Recovery curves for  $T=100$  K (red points),  $T=22$  K (green diamonds), and  $T=7$  K (blue squares) in  $H_0=7.01$  T. Normalization corresponds to a division by the prefactor  $f(=1.7-2)$  of Eq. (1). The lines are examples for the different fitting functions containing a single  $T_1$  component (solid line), a distribution around one  $T_1$  component with a stretching parameter  $\lambda$  (dashed line) and two components  $T_{1SC}$  and  $T_{1s}$  (dotted line).

A polycrystalline sample of  $\text{LaFeAs}_{1-\delta}\text{O}_{0.9}\text{F}_{0.1}$  was prepared by standard methods and characterized by x-ray diffraction, susceptibility, and resistivity measurements.<sup>25,26</sup> The As deficiency was obtained by wrapping the sample in a Ta foil during the annealing procedure leading to  $\delta=0.05-0.1$ . The increased disorder is reflected in the enhanced resistivity in the normal state compared to the clean sample.<sup>27</sup> However,  $T_c$  and the slope of  $B_{c2}(T)$  near  $T_c$  increase unexpectedly from 26.8 K and  $-2.5$  T/K in the stoichiometric compound to 28.5 K and  $-5.4$  T/K in the As-deficient compound. Muon spin relaxation ( $\mu\text{SR}$ ) measurements proved an enhanced paramagnetism, which is the origin of the observed Pauli-limiting behavior of  $B_{c2}(T)$  at lower temperatures.<sup>26</sup> The SC volume fraction is about 90% while in the pure sample it amounts to 100%.<sup>28</sup>

For the NMR experiments the sample was ground to a powder. The  $^{75}\text{As}$  NMR spectrum showed a typical powder pattern as reported previously.<sup>29</sup> The  $^{75}\text{As}$  NSLRR  $T_1^{-1}$  was measured at the peak corresponding to  $H\parallel ab$  in a magnetic field of  $H_0=7.01$  T using inversion recovery. The recovery of the longitudinal magnetization  $M_z(t)$  was fitted to the standard expression for magnetic relaxation of a nuclear spin of  $I=3/2$  which reads,

$$M_z(t) = M_0[1 - f(0.9e^{-(6t/T_1)^\lambda} + 0.1e^{-(t/T_1)^\lambda})]. \quad (1)$$

Typical recovery curves for  $T=100$  K,  $T=22$  K, and  $T=7$  K are given in Fig. 1. Above  $T_c(H_0)\approx 26$  K the recovery could be nicely fitted with a single  $T_1$  component ( $\lambda=1$ ). For  $T<T_c$  a stretching parameter  $\lambda<1$  was needed to account for a distribution of NSLR times around a characteristic relaxation time. For  $T\leq 14$  K, where the intrinsic NSLR time  $T_{1SC}$  in the SC state amounts to a few seconds,

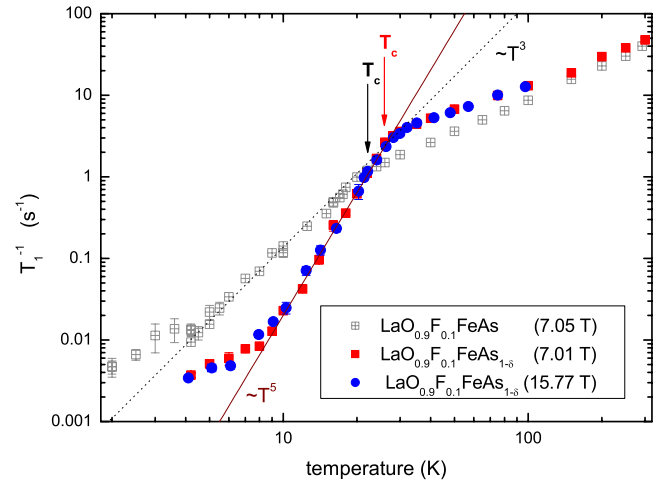


FIG. 2. (Color online)  $^{75}\text{As}$  SLRR for  $\text{LaFeAs}_{1-\delta}\text{O}_{0.9}\text{F}_{0.1}$  in 7.01 T (red squares) and 15.77 T (blue circles) compared to  $\text{LaFeAsO}_{0.9}\text{F}_{0.1}$  in 7.05 T [gray crossed squares (Ref. 29), new data points for  $T\leq 4.2$  K]. The dotted line illustrates the  $T^3$  behavior of  $T_1^{-1}$  for  $\text{LaFeAsO}_{0.9}\text{F}_{0.1}$ , the solid line indicates the  $T^5$  behavior observed for  $\text{LaFeAs}_{1-\delta}\text{O}_{0.9}\text{F}_{0.1}$ .

we could distinguish a second, short contribution  $T_{1s}$ . For this  $T$  range a fitting function containing two weighted  $T_1$  components was used. While the determination of  $T_{1s}$  was imprecise, the long time component  $T_{1SC}$ , which displays the intrinsic relaxation in the SC state, did not depend on the fitting procedure.  $T_{1s}$  lies in the range of several hundred milliseconds, indicating non-SC regions in the sample. Its weight of  $(20\pm 10)\%$  suggests, in addition to vortex cores, a minority non-SC volume fraction in agreement with  $\mu\text{SR}$  measurements. Figure 2 shows the  $T$  dependence of the  $^{75}\text{As}$  NSLRR  $T_1^{-1}$  for the As-deficient sample  $\text{LaFeAs}_{1-\delta}\text{O}_{0.9}\text{F}_{0.1}$  and that of a sample with the same F content but without As vacancies.<sup>29</sup> For the latter one, recently measured additional data points for  $T\leq 4.2$  K are shown. Very surprisingly, for  $T<T_c$  the NSLRR of  $\text{LaFeAs}_{1-\delta}\text{O}_{0.9}\text{F}_{0.1}$  decays with  $T^5$ , in contrast to the  $T^3$  dependence of  $\text{LaFeAsO}_{0.9}\text{F}_{0.1}$ . Using a field of 15.77 T this unexpected behavior was preserved within error bars, as shown in Fig. 2.

For  $T\leq 8$  K,  $T_1^{-1}$  of  $\text{LaFeAs}_{1-\delta}\text{O}_{0.9}\text{F}_{0.1}$  deviates from this  $T^5$  behavior and changes to a linear  $T$  dependence. A similar behavior is also visible for  $\text{LaFeAsO}_{0.9}\text{F}_{0.1}$  for  $T\leq 4.2$  K. These low- $T$  features with a nearly linear slope below  $T\approx 0.3T_c$  were also observed in  $\text{BaFe}_2(\text{As}_{0.67}\text{P}_{0.33})_2$  and explained with the existence of a residual density of states (RDOS) in a line-node model.<sup>30</sup> Such a high RDOS can be excluded by penetration depth data derived from  $\mu\text{SR}$  for the La-1111 samples<sup>28</sup> as well as for other pnictide systems.<sup>22</sup> Among other possible mechanisms, the classical spin diffusion<sup>31</sup> is unlikely due to the lack of field dependence of  $T_1^{-1}$ . Another possibility are thermal fluctuations of vortices, which induce alternating magnetic fields contributing to the relaxation.<sup>32</sup> Further study on a larger field range, especially at low fields, is needed to clarify this  $T_1^{-1}\propto T$  behavior.

We will now discuss the different  $T$  dependencies for  $T>0.3T_c$  within the previously mentioned scenarios. To the best of our knowledge, no exponential but power-law depen-

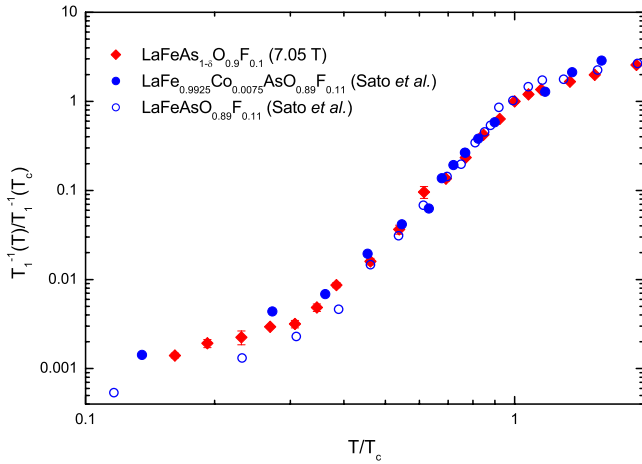


FIG. 3. (Color online) Comparison of the  $^{75}\text{As}$  NSLRR for our  $\text{LaFeAs}_{1-\delta}\text{O}_{0.9}\text{F}_{0.1}$  (red diamonds) with pure and Co-doped  $\text{LaFeAsO}_{0.89}\text{F}_{0.11}$  from Ref. 15 (open and filled circles).

dependencies  $\propto T^n$  have been observed<sup>15,29,33–43</sup> for all Fe-based pnictide superconductors, with  $n$  in between 1.5 and 6, indicating unconventional superconductivity. These power-law dependencies have been discussed within different models, such as  $s_{\pm}$ - and  $d$ -wave symmetries, including the possibility of multiple SC gaps.<sup>38–41</sup> Within the 122 family heavily overdoped compounds such as  $\text{KFe}_2\text{As}_2$  exhibit the lowest value observed so far whereas optimally or slightly underdoped compounds show the largest values. Recently, it has been suggested,<sup>15,33</sup> that the frequently observed  $T^3$  power law in the NSLRR should not be considered as an intrinsic effect but instead be attributed to some unspecified inhomogeneities in view of the missing correlation between the  $T_c$  value and the NSLRR exponent, while higher exponents would occur for cleaner samples. However, we find just the opposite behavior. In Fig. 3 we show the normalized  $T_1^{-1}(T)$  curves for our As-deficient sample and the samples from Ref. 15. Their nominal clean sample as well as the Co-doped one exhibit nearly the same  $T_1^{-1}(T)$  dependence as our As-deficient sample, whereas our clean sample exhibits the  $T^3$  dependence (see Fig. 2). In our opinion this points toward sizeable disorder in the samples of Ref. 15. This is further supported by the lowest resistivity of our clean sample compared to all others.<sup>15,26</sup> In this context a measurement of the upper critical field on the same samples would be helpful to clarify this point and to elucidate the role of impurities/vacancies in Fe-based superconductors in general.

In principle, our observation of an unusual transition from  $T^3$  to  $T^5$  with *increasing* disorder is not necessarily inconsistent with a  $s_{\pm}$ -wave SC gap though alternative scenarios should be invoked, too. Starting from the clean limit it has been shown<sup>9,44,45</sup> that within the generalized  $s_{\pm}$ -wave scenario both nodeless and nodal SC gaps might occur depending on the proximity of the doped sample to the AFM instability. In this regard, naively our finding can be interpreted in favor of a transition from the nodal to the nodeless SC gap upon adding As defects which for some reason might drive the system closer to antiferromagnetism, in accord with the slightly enhanced normal-state NSLRR and the slightly changed lattice constants<sup>26</sup> of the As-deficient sample.

However, such a simplistic point of view cannot be easily applied to pnictides as it is also known that the  $s_{\pm}$ -wave ground state is sensitive to nonmagnetic impurities. Most importantly, the intraband impurity scattering does not affect the superconductivity, since the SC gap does not change its sign within each of the bands. At the same time the scattering with large momenta which connects electron and hole pockets (interband scattering) is pair weakening and thus yields a decrease in  $T_c$  and simultaneously introduces power laws in the thermodynamics and  $1/T_1$  at intermediate temperatures. Therefore, if for some reason As vacancies act as “smart” impurities which change the ratio between the intraband and interband scattering, our observations could be also explained. These changes have to be reflected similarly also in the other thermodynamical or transport properties such as penetration depth or thermal conductivity. Unfortunately, there is no direct way to estimate the ratio of the intraband to interband scattering rates from experiments since usual characteristics like the residual resistance ratio or the mean-free path are quantities which mostly indicate the overall impurity effects but not their ratio.

Thus, the above-mentioned scenario is based on the assumption that  $s_{\pm}$ -wave order is stable and adding As vacancies either changes the proximity to the competing antiferromagnetism or/and the ratio of intraband to interband nonmagnetic impurity scattering in pnictides. There is, however, another intriguing possibility. Let us assume that there is a substantial electron-boson interaction which provides an attractive intraband potential for Cooper pairing. In this case a (weak) repulsive interband Coulomb scattering will still lead to the  $s_{\pm}$ -wave SC order in the clean limit though the attractive electron-boson interaction dominates. However, once the As vacancies change the ratio between intraband and interband impurity scattering, a transition from  $s_{\pm}$ -wave to conventional  $s_{++}$ -wave SC order may be induced. This scenario, however, still needs further experimental clarification. For example, despite the transition from  $T^3$  to  $T^5$  behavior we do not find any sign of the Hebel-Slichter peak in the latter case close to  $T_c$ . Moreover, current experimental data on the importance of the electron-phonon coupling are not very conclusive. Therefore, the intriguing possibility of high-energy charge fluctuations as well as weak electron-phonon interactions with orbital fluctuations<sup>16,17</sup> deserve more detailed studies. Another interesting point would be a detailed comparison with  $\text{FeSe}_{0.92}$ , which exhibits a  $T^3$  law for  $1/T_1$  (Ref. 46) and other Fe-based superconductors with vacancies in the polarizable subsystem.

To summarize, we present challenging NMR-experimental data on disordered As-deficient samples. We strongly believe that a future quantitative realistic theoretical description of our data within unconventional  $s_{\pm}$ -superconductivity or conventional but unusual  $s_{++}$ -superconductivity scenarios will stimulate the further development of these approaches and this way be finally helpful for the elucidation of the underlying but yet unsettled mechanism.

We thank M. Deutschmann, S. Müller-Litvanyi, R. Müller, R. Vogel, and A. Köhler for experimental support.

This work has been supported by the DFG, through FOR 538, SPP 1458 and Contract No. Be1749/12. G.L. acknowledges support from the A. v. Humboldt-Stiftung. M.M.K. acknowledges support from RFBR under Grant No. 09-02-

00127, RAS program on “Low temperature quantum phenomena” and President of Russia MK-1683.2010.2. S.L.D. thanks H. Kontani, K. Kuroki, K. Kikoin, and M. Kulić for useful discussions.

\*Present address: Department of Physics, University of Florida, Gainesville, Florida 32611, USA.

<sup>1</sup>Y. Kamihara *et al.*, *J. Am. Chem. Soc.* **130**, 3296 (2008).

<sup>2</sup>L. C. Hebel and C. P. Slichter, *Phys. Rev.* **113**, 1504 (1959).

<sup>3</sup>K. Masuda and S. Kurihara, [arXiv:0911.0528](https://arxiv.org/abs/0911.0528) (unpublished).

<sup>4</sup>B. Mitrović and K. V. Samokhin, *Phys. Rev. B* **74**, 144510 (2006).

<sup>5</sup>R. Akis and J. P. Carbotte, *Solid State Commun.* **78**, 393 (1991).

<sup>6</sup>Note that early penetration depth studies on LaFePO ( $T_c \sim 6$  K) suggested nodal superconductivity (Ref. 47), which is inconsistent with a fully gapped  $s_{\pm}$ -wave gap (Refs. 7, 8, and 10). Furthermore, recent low- $T$  studies of the thermal conductivity in BaFe<sub>2</sub>(As<sub>1-x</sub>P<sub>x</sub>)<sub>2</sub> revealed a nodal structure of the SC gap. These findings taken together with other data which are consistent with a nodeless structure point to the nonuniversality of the SC Fe-based materials.

<sup>7</sup>I. I. Mazin *et al.*, *Phys. Rev. Lett.* **101**, 057003 (2008).

<sup>8</sup>K. Kuroki *et al.*, *Phys. Rev. Lett.* **101**, 087004 (2008).

<sup>9</sup>K. Kuroki *et al.*, *Phys. Rev. B* **79**, 224511 (2009).

<sup>10</sup>A. V. Chubukov *et al.*, *Phys. Rev. B* **78**, 134512 (2008).

<sup>11</sup>S. Onari and H. Kontani, *Phys. Rev. Lett.* **103**, 177001 (2009).

<sup>12</sup>M. Kulić *et al.*, *EPL* **85**, 47008 (2009).

<sup>13</sup>S. Onari *et al.*, *Phys. Rev. B* **81**, 060504(R) (2010).

<sup>14</sup>S. C. Lee *et al.*, *J. Phys. Soc. Jpn.* **79**, 023702 (2010).

<sup>15</sup>M. Sato *et al.*, *J. Phys. Soc. Jpn.* **79**, 014710 (2010).

<sup>16</sup>H. Kontani and S. Onari, [arXiv:0912.1975](https://arxiv.org/abs/0912.1975) (unpublished).

<sup>17</sup>Y. Yanagi *et al.*, *Phys. Rev. B* **81**, 054518 (2010).

<sup>18</sup>J. Jaroszynski *et al.*, *Phys. Rev. B* **78**, 174523 (2008).

<sup>19</sup>H.-S. Lee *et al.*, *Phys. Rev. B* **80**, 144512 (2009).

<sup>20</sup>S. Haindl *et al.*, *Phys. Rev. Lett.* **104**, 077001 (2010).

<sup>21</sup>R. Khasanov *et al.*, *Phys. Rev. Lett.* **104**, 087004 (2010).

<sup>22</sup>K. Hashimoto *et al.*, *Phys. Rev. Lett.* **102**, 017002 (2009); L.

Malone *et al.*, *Phys. Rev. B* **79**, 140501(R) (2009); H. Ding *et al.*, *EPL* **83**, 47001 (2008); K. Hashimoto *et al.*, *Phys. Rev. Lett.* **102**, 207001 (2009); X. G. Luo *et al.*, *Phys. Rev. B* **80**, 140503(R) (2009).

<sup>23</sup>A. D. Christianson *et al.*, *Nature (London)* **456**, 930 (2008); S. Chi *et al.*, *Phys. Rev. Lett.* **102**, 107006 (2009); M. D. Lumsden *et al.*, *ibid.* **102**, 107005 (2009).

<sup>24</sup>B. Muschler *et al.*, *Phys. Rev. B* **80**, 180510(R) (2009).

<sup>25</sup>G. Fuchs *et al.*, *Phys. Rev. Lett.* **101**, 237003 (2008).

<sup>26</sup>G. Fuchs *et al.*, *New J. Phys.* **11**, 075007 (2009).

<sup>27</sup>A. Kondrat *et al.*, *Eur. Phys. J. B* **70**, 461 (2009).

<sup>28</sup>H. Luetkens *et al.*, *Nature Mater.* **8**, 305 (2009).

<sup>29</sup>H.-J. Grafe *et al.*, *Phys. Rev. Lett.* **101**, 047003 (2008).

<sup>30</sup>Y. Nakai *et al.*, *Phys. Rev. B* **81**, 020503(R) (2010).

<sup>31</sup>T. Saito *et al.*, *J. Magn. Magn. Mater.* **310**, 681 (2007).

<sup>32</sup>E. Ehrenfreund *et al.*, *Solid State Commun.* **7**, 1333 (1969).

<sup>33</sup>Y. Kobayashi *et al.*, *J. Phys. Soc. Jpn.* **78**, 073704 (2009).

<sup>34</sup>H. Mukuda *et al.*, *J. Phys. Soc. Jpn.* **77**, 093704 (2008).

<sup>35</sup>N. Terasaki *et al.*, *J. Phys. Soc. Jpn.* **78**, 013701 (2009).

<sup>36</sup>Y. Nakai *et al.*, *J. Phys. Soc. Jpn.* **77**, 073701 (2008).

<sup>37</sup>H. Fukazawa *et al.*, *J. Phys. Soc. Jpn.* **78**, 033704 (2009).

<sup>38</sup>K. Matano *et al.*, *EPL* **83**, 57001 (2008).

<sup>39</sup>S. Kawasaki *et al.*, *Phys. Rev. B* **78**, 220506(R) (2008).

<sup>40</sup>K. Matano *et al.*, *EPL* **87**, 27012 (2009).

<sup>41</sup>M. Yashima *et al.*, *J. Phys. Soc. Jpn.* **78**, 103702 (2009).

<sup>42</sup>F. Ning *et al.*, *J. Phys. Soc. Jpn.* **77**, 103705 (2008).

<sup>43</sup>S. W. Zhang *et al.*, *Phys. Rev. B* **81**, 012503 (2010).

<sup>44</sup>T. A. Maier *et al.*, *Phys. Rev. B* **79**, 224510 (2009).

<sup>45</sup>A. V. Chubukov *et al.*, *Phys. Rev. B* **80**, 140515(R) (2009).

<sup>46</sup>H. Kotegawa *et al.*, *J. Phys. Soc. Jpn.* **77**, 113703 (2008).

<sup>47</sup>J. D. Fletcher *et al.*, *Phys. Rev. Lett.* **102**, 147001 (2009).